

44th Solid Mechanics Conference



Book of Abstracts

Editors:

Katarzyna Kowalczyk-Gajewska

Jerzy Pamin

Michał Kursa

Co-editors:

Marzena Mucha

Paweł Hołobut

September 7–10, 2026

Kraków, Poland

Published by
Institute of Fundamental Technological Research
Polish Academy of Sciences
Pawińskiego 5B, 02-106 Warsaw, Poland
www.ippt.pan.pl

solmech2026.ippt.pan.pl

ISBN 978-83-65550-69-9

<https://doi.org/10.24423/solmech2026>

Copyright ©2026 by Institute of Fundamental Technological Research,
Polish Academy of Sciences,
Warsaw, Poland

Session TS7

Experimental mechanics

Orientation-Dependent Yield Surface Evolution and Anisotropic Plasticity in LPBF-Manufactured SS316L

Ved Prakash Dubey^{1,*}, Mateusz Kopec^{1,2}, Paul Wood² and Zbigniew L. Kowalewski¹

¹Institute of Fundamental Technological Research, Polish Academy of Sciences, Warsaw, Poland
e-mail: vdubey@ippt.pan.pl

²Institute for Innovation in Sustainable Engineering, College of Science and Engineering, University of Derby, United Kingdom

KEYWORDS: Additive manufacturing, Laser powder bed fusion (LPBF), Yield surface, Multiaxial loading.

The rapid adoption of laser powder bed fusion (LPBF) for stainless steel 316L (SS316L) components necessitates a deeper understanding of anisotropic plasticity under complex loading conditions [1]. This study presents a comprehensive experimental investigation of the initial and evolving yield surfaces of LPBF-fabricated SS316L, explicitly addressing the influence of printing orientation and plastic pre-deformation. Tubular specimens were manufactured in three orientations (XY, ZX45 and Z) and subjected to multiaxial loading using a single-specimen probing methodology, enabling efficient and precise yield surface characterization in axial–shear stress space.

Yield surfaces were determined using Szczepiński anisotropic yield criterion at initial state and subsequently tracked after controlled tensile plastic pre-strain equal to 0.35%, 0.5% and 0.8%. The results reveal pronounced anisotropy in LPBF specimens, strongly governed by build orientation. The Z-oriented samples exhibit reduced yield strength and enhanced softening in yield loci, while XY and ZX45 orientations demonstrate comparatively higher yield strength under selected loading paths. Additionally, specimens exhibit orientation-dependent yield surface translation and rotation, indicating complex interactions between strain-induced hardening/softening mechanisms and inherent microstructural anisotropy [2].

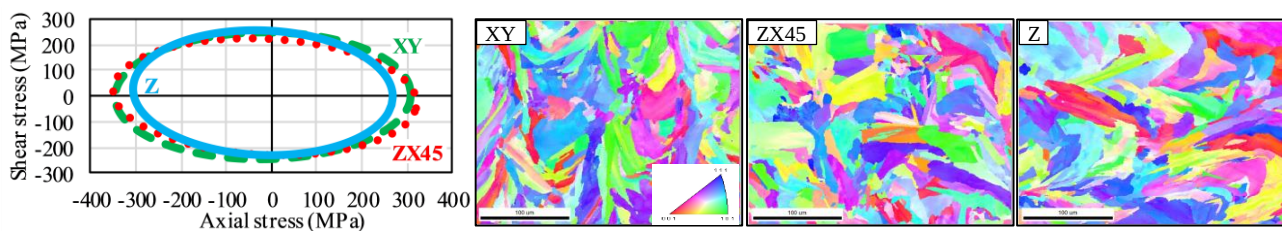


Figure 1. Initial yield surfaces at 10µε offset definition of yield and IPF maps of three printing orientations.

Microstructural analysis using electron backscatter diffraction (EBSD) establishes a strong correlation between grain morphology and mechanical anisotropy. Columnar grains aligned along the build direction in Z-oriented samples promote directional deformation and strain localization, whereas more equiaxed structures in XY and ZX orientations contribute to improved mechanical uniformity. Despite weak crystallographic texture, melt pool geometry and interlayer boundaries emerge as primary drivers of anisotropic plastic response.

ACKNOWLEDGEMENT: This work was funded by the National Science Centre, Poland through the grant no. 2023/51/B/ST8/01751.

- [1] V.P. Dubey, D. Przygucka, M. Pawlik, Z.L. Kowalewski, P. Wood and M. Kopec, *Materials Today Communications* **50**, 114531, 2026. <https://doi.org/10.1016/j.mtcomm.2025.114531>
- [2] V.P. Dubey, M. Kopec, D. Przygucka, M. Pawlik, P. Wood and Z.L. Kowalewski, *Int. J. Adv. Manuf. Technol.* **140**, 313–334, 2025. <https://doi.org/10.1007/s00170-025-16296-y>